



## ORIGINAL ARTICLE

# Nano-silica sulfuric acid as an efficient catalyst for the synthesis of substituted pyrazoles



Hamideh Emtiazi, Mohammad Ali Amrollahi \*, Bi Bi Fatemeh Mirjalili

Department of Chemistry, College of Science, Yazd University, P.O. Box 89195-741, Yazd, Iran

Received 28 September 2012; accepted 9 June 2013

Available online 19 June 2013

## KEYWORDS

Trisubstituted pyrazoles;  
Nano silica sulfuric acid;  
Hydrazines;  
1,3-Diketones

**Abstract** A convenient and direct approach has been developed for the preparation of pyrazole derivatives by condensing 1,3-diketones and hydrazines in the presence of nano-silica sulfuric acid. This thermal solvent-free procedure offers some advantages such as short reaction time, simple work-up, high yields, and reusability of the catalyst.

© 2013 Production and hosting by Elsevier B.V. on behalf of King Saud University.

## 1. Introduction

The synthesis of nitrogen-containing heterocyclic compounds has been a subject of great interest due to their wide application in agrochemical and pharmaceutical fields (Noga et al., 1986; Craig, 1991). Pyrazole derivatives, which belong to this category, fulfill a wide variety of biological functions such as antipyretic (Behr et al., 1967), antibacterial (Mahajan et al., 1991), antipsychotic (Barcelo et al., 2007), antiviral (Larsen et al., 1999), pesticidal (Londershausen, 1996), and insecticidal ones (Windholz, 1976).

Pyrazoles can be synthesized *via* 1,3-dipolar cycloadditions of diazo compounds (Aggarwal et al., 2003), reaction of chalcones and hydrazines (Bhat et al., 2005), a three-component coupling of hydrazine, aldehyde and ethyl acetoacetate

(Kumari et al., 2012), reaction of isocyanides, dialkylacetylenedicarboxylates and diacylhydrazines (Adib et al., 2005), and the direct condensation of 1,3-diketones and hydrazines in the presence of an acidic catalyst (Fustero et al., 2008; Katritzky, 1985). The last one is the most straightforward procedure for the synthesis of pyrazole derivatives. This procedure can be carried out in the presence of various catalysts such as H<sub>2</sub>SO<sub>4</sub> (Wang and Qin, 2004), polystyrene-supported sulfonic acid (Polshettiwar and Varma, 2008), layered zirconium sulfophenyl phosphonate [a-Zr(CH<sub>3</sub>PO<sub>3</sub>)<sub>1.2</sub>(O<sub>3</sub>PC<sub>6</sub>H<sub>4</sub>SO<sub>3</sub>H)<sub>0.8</sub>] (Curini et al., 2005), Sc(OTf)<sub>3</sub> (Xiong et al., 2009), Y-zeolite (Sreekumar and Padmakumar, 1998), and Mg(ClO<sub>4</sub>)<sub>2</sub> (Mirjalili et al., 2010).

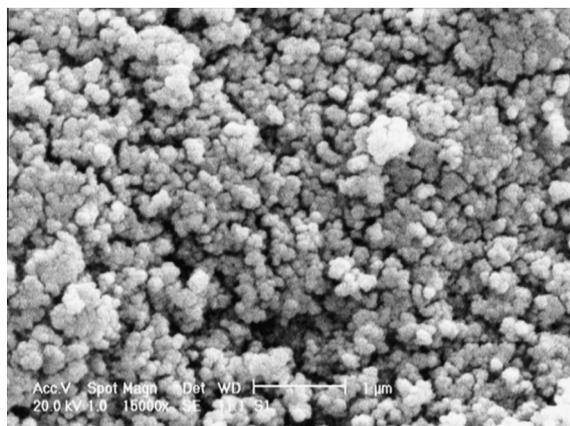
In recent years, the use of reusable heterogeneous catalysts has received considerable importance in organic synthesis. This is because of their environmental, economic, and industrial benefits. Among these, the application of silica sulfuric acid (SSA) or nano-silica sulfuric acid (nano-SSA), which is a stable and efficient heterogeneous catalyst in organic synthesis, has been widely studied. This catalyst is important from an environmental point of view because it produces little waste. It also has an excellent activity and selectivity even on an industrial scale and, in most cases, can be recovered from reaction mixtures and reused.

\* Corresponding author. Tel.: +98 3517256129.

E-mail address: mamrollahi@yazduni.ac.ir (M.A. Amrollahi).

Peer review under responsibility of King Saud University.





**Figure 1** The SEM photograph of nano-SSA.

Silica sulfuric acid has already gained much interest in the synthesis of substituted pyrroles (Veisi, 2010),  $\beta$ -aminoketones (Wu et al., 2007), N-acylsulfonamides (Massah et al., 2008), triarylmethanes (Mohammad poor-Baltork et al., 2011), imidazo pyridines (Polyakov et al., 2009), and deprotection of oximes to carbonyls (Li et al., 2010). Now, we report an efficient and convenient procedure for the synthesis of substituted pyrazoles using silica sulfuric acid or nano-silica sulfuric acid as a catalyst.

## 2. Materials and methods

The products were characterized by elemental analysis, IR,  $^1\text{H-NMR}$ , and  $^{13}\text{C-NMR}$  spectra. IR spectra were run on a Bruker, Equinox 55 spectrometer.  $^1\text{H-NMR}$  and  $^{13}\text{C-NMR}$  spectra were obtained using a Bruker Avance 400 and 500 MHz spectrometers (DRX). The elemental analysis was done by a Costech ECS 4010 CHNS-O analyzer. The melting points were measured by a Buchi melting point B-540 apparatus and the SEM of nano-SSA particles was determined with a VEGA/TESCAN scanning electron microscope.

### 2.1. Synthesis of nano-SSA

A 500 mL suction flask containing nano-silica gel (60.0 g) was equipped with a constant pressure dropping funnel containing chlorosulfonic acid (23.3 g, 0.2 mol) and gas inlet tube for conducting HCl gas over an adsorbing solution i.e., water. Chlorosulfonic acid was added dropwise over a period of 30 min at room temperature. HCl gas was evolved from the reaction vessel immediately. After the addition was complete, the mixture was shaken for 30 min and a white solid of nano-SSA (76.0 g) was collected. Fig. 1 is the SEM photograph of the product. The SSA was prepared according to the literature (Zolfigol, 2001).

### 2.2. General procedure for the synthesis of pyrazole derivatives

1,3-Diketone (1 mmol), substituted hydrazine (1 mmol), and silica sulfuric acid (0.06 g) or nano-silica sulfuric acid (0.01 g) were placed in a round bottom flask that was heated at 60 °C. The progress of the reaction was followed by TLC.

After the completion of the reaction, the product was dissolved to chloroform and filtered to recover the catalyst. The solvent was evaporated, and the crude mixture was solidified from a mixture of ethanol and water. The pure product was obtained by recrystallization in ethanol. The products were characterized on the basis of spectroscopic data. The  $^1\text{H-NMR}$  spectrum of product consisted one singlet for pyrazole ring C–H ( $\delta = 6.92$ ), a doublet for 2 ortho protons of 5-phenyl ring ( $\delta = 7.30$ ), a multiplet for 6 para and meta protons of phenyl rings ( $\delta = 7.40\text{--}7.50$ ), a doublet for 2 ortho protons of 3-phenyl ring ( $\delta = 8.05$ ), two doublets and one singlet for 3 protons of 2,4-dinitrophenyl ring ( $\delta = 8.15, 8.80, 8.95$ ). The  $^{13}\text{C-NMR}$  spectrum exhibited 17 sharp signals in agreement with the proposed structure.

### 2.3. Some selected spectroscopic data

#### 2.3.1. 1-(2,4-Dinitrophenyl)-3,5-diphenyl-1H-pyrazole (Table 2, entry 3)

IR: 1607, 1536, 1491, 1459, 1344, 1076, 832, 762, 691.  $^1\text{H-NMR}$  (500 MHz,  $\text{CDCl}_3$ ): 6.92 (s, 1 H); 7.30 (d, 2 H,  $J = 6.0$  Hz); 7.40–7.50 (m, 6 H); 8.05 (d, 2 H,  $J = 5.7$  Hz); 8.15 (d, 1 H,  $J = 7.2$ ); 8.80 (d, 1 H,  $J = 6.8$  Hz); 8.95 (s, 1H).  $^{13}\text{C-NMR}$  (125 MHz,  $\text{CDCl}_3$ ): 107.21; 121.47; 126.45; 127.42; 129.19; 129.28; 129.35; 129.57; 129.92; 130.55; 132.27; 138.53; 143.32; 145.61; 146.36; 146.42; 155.34. Anal. calcd. for  $\text{C}_{21}\text{H}_{14}\text{N}_4\text{O}_4$ : C 65.28, H 3.65, N 14.50; Found: C 64.98, H 3.55, N 14.40.

#### 2.3.2. 4-Chloro-1-(2,4-dinitrophenyl)-3,5-dimethyl-1H-pyrazole (Table 2, entry 4)


IR: 1607, 1529, 1480, 1344, 1104, 1029, 903, 848, 834, 795.  $^1\text{H-NMR}$  (500 MHz,  $\text{CDCl}_3$ ): 2.30 (s, 3 H); 2.47 (s, 3 H); 8.10 (d, 1 H,  $J = 8.8$  Hz); 8.57 (dd, 1 H,  $J = 8.8$  Hz,  $J = 2.4$  Hz); 8.83 (d, 1 H,  $J = 2.4$  Hz).  $^{13}\text{C-NMR}$  (125 MHz,  $\text{CDCl}_3$ ): 10.61; 11.87; 112.73; 121.67; 127.98; 129.73; 137.54; 137.97; 142.82; 145.64; 149.92. Anal. calcd. for  $\text{C}_{11}\text{H}_9\text{ClN}_4\text{O}_4$ : C 44.53, H 3.06, N 18.89; Found: C 44.60, H 3.30, N 18.70.

#### 2.3.3. 1-(4-Bromophenyl)-4-chloro-3,5-dimethyl-1H-pyrazole (Table 2, entry 8)

IR: 1588, 1500, 1470, 1401, 1380, 1366, 1099, 1070, 1037, 1008, 831, 810, 795.  $^1\text{H-NMR}$  (500 MHz,  $\text{CDCl}_3$ ): 2.33 (s, 3 H); 2.65 (s, 3 H); 7.54 (d, 2H,  $J = 8.4$  Hz); 7.85 (d, 2H,  $J = 8.4$  Hz).  $^{13}\text{C-NMR}$  (125 MHz,  $\text{CDCl}_3$ ): 10.83; 11.35; 121.31; 125.58; 125.85; 132.34; 132.39; 138.72; 146.51. Anal. calcd. for  $\text{C}_{11}\text{H}_{10}\text{BrClN}_2$ : C 46.26, H 3.53, N 9.81; Found: C 46.50, H 3.32, N 10.05.

#### 2.3.4. 3,5-Diphenyl-1-(4-methylphenyl)-1H-pyrazole (Table 2, entry 11)

IR (ATR, neat): 1604, 1545, 1511, 1480, 1361, 972, 822, 760, 691.  $^1\text{H-NMR}$  (400 MHz,  $\text{CDCl}_3$ ): 2.38 (s, 3 H); 6.83 (s, 1 H); 7.16 (d, 2 H,  $J = 8.4$  Hz); 7.30 (m, 6H); 7.44 (t, 2 H,  $J = 7.6$  Hz); 7.93 (dd, 2 H,  $J = 7.8$  Hz,  $J = 1.2$  Hz), 8.10 (d, 2 H,  $J = 8.0$  Hz).  $^{13}\text{C-NMR}$  (100 MHz,  $\text{CDCl}_3$ ): 21.11; 105.22; 125.29; 125.83; 128.05; 128.39; 128.55; 128.79; 128.92; 129.57; 130.69; 133.10; 137.52; 137.73; 142.55; 149.32. Anal. calcd. for  $\text{C}_{22}\text{H}_{18}\text{N}_2$ : C 85.13, H 5.58, N 9.03; Found: C 85.20, H 5.81, N 8.75.

**Table 1** Condensation of 1, 3-diphenyl-1, 3-propanedione with phenylhydrazine under different reaction conditions<sup>a</sup>


Entry	Catalyst (g)	Solvent	Conditions	Time (h)	Yield (%)	Ref.
1	–	Solvent-free	60 °C	2	25	–
2	SSA(0.02)	Solvent-free	r.t	0.5	40	–
3	SSA(0.02)	Solvent-free	60 °C	0.5	68	–
4	SSA(0.04)	Solvent-free	r.t	0.5	45	–
5	SSA(0.04)	Solvent-free	60 °C	0.5	78	–
6	SSA(0.06)	Solvent-free	r.t	0.5	52	–
7	SSA(0.06)	Solvent-free	60 °C	0.5	86	–
8	SSA(0.08)	Solvent-free	r.t	0.5	52	–
9	SSA(0.08)	Solvent-free	60 °C	0.5	88	–
10	Nano-SSA(0.002)	Solvent-free	60 °C	0.5	68	–
11	Nano-SSA(0.006)	Solvent-free	60 °C	0.5	82	–
12	Nano-SSA(0.01)	Solvent-free	60 °C	0.5	93	–
13	Nano-SSA(0.014)	Solvent-free	60 °C	0.5	95	–
14	Nano-SSA(0.01)	Water	60 °C	5	30	–
15	Nano-SSA(0.01)	Ethanol	60 °C	1	80	–
16	Nano-SSA(0.01)	Acetonitrile	60 °C	3	75	–
17	Nano-SSA(0.01)	Ethyl acetate	60 °C	3	70	–
18	Nano-SSA(0.01)	Chloroform	60 °C	3	60	–
19	Nano-SSA(0.01)	Dichloromethane	60 °C	3	55	–
20	Nano-SSA(0.01)	<i>n</i> -Hexane	60 °C	5	40	–
21	SSA(0.01), 2nd run	Solvent-free	60 °C	0.5	76	–
22	H <sub>2</sub> SO <sub>4</sub> (0.1 drop)	Solvent-free	r.t	1	86	Wang and Qin (2004)
23	Polystyrene supported sulfonic acid (0.1 mL of 20% PSSA solution)	Solvent-free	r.t	0.04	92	Polshettiwar et al. (2008)
24	[ <i>a</i> -Zr(CH <sub>3</sub> PO <sub>3</sub> ) <sub>1.2</sub> (O <sub>3</sub> PC <sub>6</sub> H <sub>4</sub> SO <sub>3</sub> H) <sub>0.8</sub> ](0.025)	Solvent-free	40 °C	2	95	Curini et al. (2005)
25	Sc(OTf) <sub>3</sub> (2 mol%)	Solvent-free	r.t	0.35	94	Xiong et al. (2009)
26	Y-Zeolite (1)	Ethylene dichloride	r.t 2		84	Sreekumar and Padmakumar (1998)

<sup>a</sup> 1, 3-Diphenyl-1, 3-propanedione (1 mmol) and Phenylhydrazine (1 mmol) were applied.

### 2.3.5. 3,5-Diphenyl-1-(4-tolulosulfonyl)-1H-pyrazole (Table 2, entry 16)

IR: 1594, 1557, 1484, 1458, 1379, 1191, 1174, 1101, 942, 759, 684, 658. <sup>1</sup>H NMR (400 MHz, CDCl<sub>3</sub>): 2.20 (s, 3 H); 6.81 (s, 1H); 7.40–7.60 (m, 8H); 7.80 (m, 4 H); 8.13 (d, 2 H, *J* = 7.8 Hz). <sup>13</sup>C-NMR (100 MHz, CDCl<sub>3</sub>): 21.52; 106.46; 127.32; 127.55; 128.34; 128.72; 129.10; 129.43; 129.68; 130.45; 130.59; 132.73; 133.96; 144.51; 146.22; 146.78. Anal. calcd. for C<sub>22</sub>H<sub>18</sub>N<sub>2</sub>O<sub>2</sub>S: C 70.57, H 4.85, N 7.48; Found: C 70.25, H 5.10, N 7.70.

### 2.3.6. 3-Methyl-5-phenyl-1-(4-tolulosulfonyl)-1H-pyrazole (Table 2, entry 17)

IR: 1593, 1563, 1459, 1375, 1294, 1278, 1190, 1122, 1076, 811, 767, 688, 670. <sup>1</sup>H-NMR (400 MHz, CDCl<sub>3</sub>): 2.32 (s, 3 H); 2.40 (s, 3 H); 6.40 (s, 1 H); 7.32 (d, 2 H, *J* = 8.2 Hz); 7.43 (m, 3 H); 7.81 (d, 2 H, *J* = 6.8 Hz); 7.90 (d, 2 H, *J* = 8.2 Hz). <sup>13</sup>C-NMR (100 MHz, CDCl<sub>3</sub>): 10.58; 23.42; 105.43; 126.49; 127.31; 127.95; 128.53; 128.92; 131.31; 132.12; 135.25; 143.58; 149.43. Anal. calcd. for C<sub>17</sub>H<sub>16</sub>N<sub>2</sub>O<sub>2</sub>S: C 65.36, H 5.16, N 8.97; Found: C 65.25, H 5.10, N 7.27.

### 2.3.7. 1,3,5-Triphenyl-4,5-dihydro-1H-pyrazole (Scheme 2)

IR: 1596, 1503, 1393, 1325, 1268, 1124, 874, 758, 745, 692. H NMR (400 MHz, CDCl<sub>3</sub>): 3.16 (dd, 1H, *J* = 12.4 and

7.6 Hz), 3.86 (dd, 1H, *J* = 14.4 and 12.4 Hz), 5.29 (dd, 1H, *J* = 14.4 and 7.6 Hz), 7.00–7.50 (m, 12H), 7.80 (brs, 2H). <sup>13</sup>C-NMR (100 MHz, CDCl<sub>3</sub>): 115.43; 118.48; 125.14; 126.52; 127.51; 127.97; 128.32; 129.22; 129.63; 130.50; 130.91; 131.65; 135.32; 136.83; 140.72.

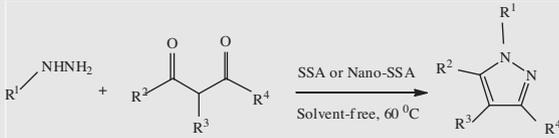
### 2.3.8. Ethyl 3-(2-(2,4-dinitrophenyl)hydrazono) butanoate

IR: 1726, 1614, 1506, 1420, 1342, 1314, 1104, 834. <sup>1</sup>H-NMR (500 MHz, CDCl<sub>3</sub>): 1.35 (t, *J* = 7.1 Hz, 3H); 2.21 (s, 3H); 3.52(s, 2H); 4.27 (q, 2H, *J* = 7.1 Hz); 8.01 (d, 1H, *J* = 9.5 Hz); 8.36 (dd, 1H, *J* = 9.5 and 2.5 Hz); 9.17 (d, 1H, *J* = 2.5 Hz); 11.13 (s, NH). <sup>13</sup>C-NMR (125 MHz, CDCl<sub>3</sub>): 14.62; 16.65; 44.97; 61.93; 116.91; 123.82; 130.57; 132.54; 138.67; 145.45; 151.12; 169.67.

## 3. Results and discussion

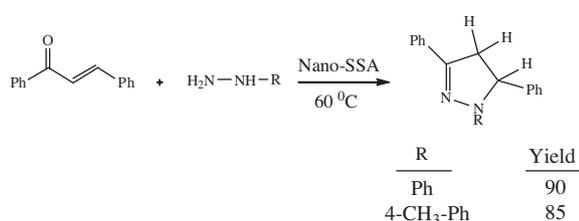
In order to optimize the reaction conditions, we studied the condensation of 1,3-diphenyl-1, 3-propanedione (1 mmol) with phenylhydrazine (1 mmol) in various reaction conditions. The results are summarized in Table 1.

Initially, the reaction was performed with different amounts of SSA in various conditions. It was found that 0.06 g of SSA as a catalyst would be sufficient and an excessive amount of that would not increase the yield remarkably (Table 1, entry

**Table 2** The condensation of 1, 3-diketones and hydrazines in the presence of silica sulfuric acid or nano-silica sulfuric acid<sup>a</sup>


Entry	R <sup>1</sup>	R <sup>2</sup>	R <sup>3</sup>	R <sup>4</sup>	Yield (%)	Nano-SSA/SSA	Time (min)	Mp (°C) [m.p. reported]	Ref.
1	2,4- O <sub>2</sub> N-C <sub>6</sub> H <sub>3</sub>	CH <sub>3</sub>	H	CH <sub>3</sub>	85/79		15	122–124	Xiong et al. (2009)
2	2,4- O <sub>2</sub> N-C <sub>6</sub> H <sub>3</sub>	C <sub>6</sub> H <sub>5</sub>	H	CH <sub>3</sub>	92/93		20	127–129	Curini et al. (2005)
3	2,4- O <sub>2</sub> N-C <sub>6</sub> H <sub>3</sub>	C <sub>6</sub> H <sub>5</sub>	H	C <sub>6</sub> H <sub>5</sub>	92/90		20	149–150	Mirjalili et al. (2010)
4	2,4- O <sub>2</sub> N-C <sub>6</sub> H <sub>3</sub>	CH <sub>3</sub>	Cl	CH <sub>3</sub>	89/80		25	166–168	Mirjalili et al. (2010)
5	C <sub>6</sub> H <sub>5</sub>	C <sub>6</sub> H <sub>5</sub>	H	C <sub>6</sub> H <sub>5</sub>	93/86		30	137–138	Sreekumar and Padmakumar (1998)
6	C <sub>6</sub> H <sub>5</sub>	CH <sub>3</sub>	Cl	CH <sub>3</sub>	93/86		20	Oil	Polshettiwar et al. (2008)
7	H	C <sub>6</sub> H <sub>5</sub>	H	CH <sub>3</sub>	87/87		25	202–204	Mirjalili et al. (2010)
8	4- Br-C <sub>6</sub> H <sub>4</sub>	CH <sub>3</sub>	Cl	CH <sub>3</sub>	94/90		15	87–88	Mirjalili et al. (2010)
9	4- Br-C <sub>6</sub> H <sub>4</sub>	C <sub>6</sub> H <sub>5</sub>	H	C <sub>6</sub> H <sub>5</sub>	90/85		40	119–120	Mirjalili et al. (2010)
10	4- Br-C <sub>6</sub> H <sub>4</sub>	C <sub>6</sub> H <sub>5</sub>	H	CH <sub>3</sub>	92/88		25	178–180	Mirjalili et al. (2010)
11	4- Me-C <sub>6</sub> H <sub>4</sub>	C <sub>6</sub> H <sub>5</sub>	H	C <sub>6</sub> H <sub>5</sub>	87/94		40	104–105	Mirjalili et al. (2010)
12	4- Me-C <sub>6</sub> H <sub>4</sub>	C <sub>6</sub> H <sub>5</sub>	H	CH <sub>3</sub>	89/87		15	82–84	Mirjalili et al. (2010)
13	4-OMe-C <sub>6</sub> H <sub>4</sub>	C <sub>6</sub> H <sub>5</sub>	H	C <sub>6</sub> H <sub>5</sub>	74/78		30	oil	Mirjalili et al. (2010)
14	4-OMe-C <sub>6</sub> H <sub>4</sub>	C <sub>6</sub> H <sub>5</sub>	H	CH <sub>3</sub>	88/88		20	oil	Mirjalili et al. (2010)
15	4- Me-C <sub>6</sub> H <sub>4</sub> SO <sub>2</sub>	CH <sub>3</sub>	H	CH <sub>3</sub>	83/80		20	94–95	Xiong et al. (2009)
16	4- Me-C <sub>6</sub> H <sub>4</sub> SO <sub>2</sub>	C <sub>6</sub> H <sub>5</sub>	H	C <sub>6</sub> H <sub>5</sub>	83/85		25	101–103	Mirjalili et al. (2010)
17	4- Me-C <sub>6</sub> H <sub>4</sub> SO <sub>2</sub>	C <sub>6</sub> H <sub>5</sub>	H	CH <sub>3</sub>	84/85		35	86–87	Mirjalili et al. (2010)

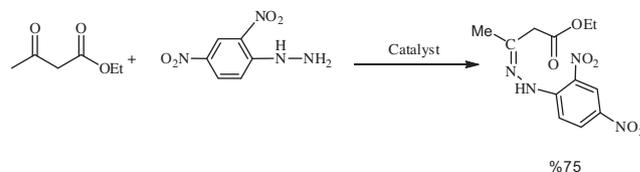
<sup>a</sup> Phenylhydrazine (1 mmol), 1, 3-Diphenyl-1, 3-propanedione (1 mmol) silica sulfuric acid (0.06 g) or nano-silica sulfuric acid (0.01 g).

**Scheme 1**

7). We repeated the above mentioned reaction with various amounts of nano-SSA with the finding that the activity of nano-SSA is six times more, and only 0.01 g of it would be sufficient (Table 1, entry 12). Among the various reaction conditions (Table 1, entries 1–20), the most effective condition in terms of reaction yield and rate was found to be created by SSA (0.06 g) and nano-SSA (0.01 g) in solvent-free media at 60 °C. The nano-SSA is a more effective activation agent because of the wide surface of it and can accelerate the overall reaction rate by a little amount of it.

To examine the reusability of nano-SSA under a solvent-free condition, after each run, the product was dissolved to CHCl<sub>3</sub> and filtered. The catalyst residue was washed with acetone and reused. As a matter of fact, treatment with acetone removes the tar from the catalyst surface more efficiently (Table 1, entry 21). The catalyst was reusable although a gradual decline was observed in its activity.

The general efficiency of this protocol was then studied for the synthesis of a variety of pyrazoles (Table 2). As it can be seen in Table 2, various hydrazines reacted efficiently with 1,3-diketones to afford the desired pyrazoles in good yields. Investigation was made of a series of aromatic hydrazines

**Scheme 2**

bearing either electron-donating or electron-withdrawing groups on the aromatic ring. The substitution group on the phenyl ring seemed to affect the reaction significantly neither in the product yield nor in the reaction rate.

The reactions of chalcone with hydrazines in the presence of nano-silica sulfuric acid were examined and the corresponding products were produced in high yields (Scheme 1).

Ethylacetoacetate was utilized as substrate and the pyrazole ring was not formed (Scheme 2).

#### 4. Conclusions

This paper reports the development of an efficient procedure for the synthesis of substituted pyrazoles using nano-silica sulfuric acid as a reusable, eco-friendly and efficient heterogeneous catalyst. The major advantages of this procedure include easy work-up, high yields, clean reactions, and low catalyst loading.

#### Acknowledgement

Authors thank the Research Council of Yazd University for the financial support.

**References**

- Adib, M., Sayahi, M.H., Rahbari, S., 2005. *Tetrahedron Lett.* 46, 6545.
- Aggarwal, V.K., Vicente, D.V., Bonnert, R.V., 2003. *J. Org. Chem.* 68, 5381.
- Barcelo, M., Ravina, E., Masaguer, C.F., Dominuez, E., Areias, F.M., Brea, J., Loza, M.I., 2007. *Bioorg. Med. Chem. Lett.* 17, 4873.
- Behr, L.C., Fusco, R., Jarboe, C.H., 1967. In: Weissberger, A. (Ed.), *The Chemistry of Heterocyclic Compounds Pyrazoles Pyrazolines Pyrazolidines Indazoles and Condensed Rings*. Interscience Publishers, New York, p. 1.
- Bhat, B.A., Puri, S.C., Qurishi, M.A., Dhar, K.L., Qazi, G.N., 2005. *Synth. Commun.* 35, 1135.
- Curini, M., Rosati, O., Campagna, V., Montanari, F., Cravotto, G., Boccalini, M., 2005. *Synlett* 19, 2927.
- Fustero, S., Román, R., Sanz-Cervera, J.F., Simón-Fuentes, X.A., Cuñat, A.C., Murguía, M., Villanova, S., 2008. *J. Org. Chem.* 73, 3523.
- Katritzky, A.R., 1985. *Handbook of Heterocyclic Chemistry*. Pergamon, New York, p. 416.
- Kumari, K., Raghuvanshi, D.S., Jouikov, V., Sing, K.N., 2012. *Tetrahedron Lett.* 53, 1130.
- Larsen, J.S., Zahran, M.A., Pedersen, E.B., Nielsen, C., 1999. *Monatsh. Chem.* 130, 1167.
- Li, J., Meng, X., Bai, B., Sun, M., 2010. *Ultrason. Sonochem.* 17 (1), 14–16.
- Londershausen, M., 1996. *Pestic. Sci.* 48, 269.
- Mahajan, R.N., Havaladar, F.H., Fernandes, P.S., 1991. *J. Indian Chem. Soc.* 68, 245.
- Massah, A.R., Adibi, H., Khodarahmi, R., Abiri, R., Majnooni, M.B., Shahidi, S., 2008. *Bioorg. Med. Chem.* 16, 5465.
- Mirjalili, B.B.F., Bamoniri, A., Amrollahi, M.A., Emtiazi, H., 2010. *Dig. J. Nanomater. Biostruct.* 5, 897.
- Mohammad poor-Baltork, I., Moghadam, M., Tangestaninejad, S., Mirkhani, V., Mohammadiannejad Abbasabadi, K., Zolfigol, M.A., 2011. *C. R. Chimie* 14, 934.
- Noga, E.J., Barthalmus, G.T., Mitchell, M.K., 1986. *Cell Biol. Int. Rep.* 10, 239.
- Craig, P.N., . In: Drayton, C.J. (Ed.), *In: Comprehensive Medicinal Chemistry*, vol. 8. Pergamon Press, New York.
- Polshettiwar, V., Varma, R.S., 2008. *Tetrahedron Lett.* 49, 397.
- Polyakov, A., Eryomina, V., Medvedeva, L., Tihonova, N., 2009. *Tetrahedron Lett.* 50 (30), 4389.
- Sreekumar, R., Padmakumar, R., 1998. *Synth. Commun.* 28, 1661.
- Veisi, H., 2010. *Tetrahedron Lett.* 51, 2109.
- Wang, Z., Qin, H., 2004. *Green Chem.* 6, 90.
- Windholz, M., 1976. *The Merck Index*, 9th ed. Merck and Co., Rahway, New Jersey, 8851.
- Wu, H., Shen, Y., Fan, L., Wan, Y., Zhang, P., Chen, C., Wang, W., 2007. *Tetrahedron* 63 (11), 2404.
- Xiong, W., Chen, J.-X., Liu, M.-C., Ding, J.-C., Wu, H.-Y., Su, W.-K., 2009. *J. Braz. Chem. Soc.* 20, 367.
- Zolfigol, M.A., 2001. *Tetrahedron* 57, 9509.